

WHA YU INDUSTRIAL CO., LTD.(HEAD OFFICE)
TAI HWA ELECTRONIC CO., LTD.(CHINA)
SHANGHAI HUA YU ELECTRONIC CO., LTD.(CHINA)
AEON TECH CO., LTD.(CHINA)

SPECIFICATION FOR APPROVAL

CUSTOMER: 深圳市普聯技術有限公司

PART NAME: RF Antenna Assembly

PART NO.: 31010006

REVISION:

W. Y. P/NO.: C636-510011-A

REV.: B

SSR-00193

	MANUFACTURER SIGNATURE	CUSTOMER SIGNATURE
APPROVED BY :		
DATE :		

WHA YU GROUP

WHA YU INDUSTRIAL CO., LTD.(HEAD OFFICE)

譚裕實業股份有限公司

Address: #70 Shui Li Road, Hsin Chu City, Taiwan, R.O.C.

Tel: +886-3-5714225(REP.)

Fax: + 886-3-5713853 · + 886-3-5723600

TAI HWA ELECTRONIC CO., LTD. (CHINA)

台樺電業製品廠

Address: Pak Ho District, Hou Street Town, Dong Guan City, Guangdong, China

Tel: + 86-769-5599375 · + 86-769-5912375

Fax: + 86-769-5599376

HUA HONG INTERNATIONAL LTD.

華弘國際有限公司

Rm.1103A, President Commercial Centre, 608 Nathan Road, Mong Kok, Kowloon, Hong Kong

Tel: + 86-852-27712210

Fax: + 86-852-23843747

SHANGHAI HUA YU ELECTRONIC CO., LTD. (CHINA)

上海譚裕電子有限公司

Address: 3586, Wai Qing Song Road, Qing Pu County, Shanghai China

Tel: + 86-21-59741348 · + 86-21-59744101~4

Fax: + 86-21-59741347

SU ZHOU AEON TECH CO., LTD. (CHINA)

蘇州華廣電通有限公司

Address: Limin North Road, LiLi Town, LiLi Industrial Park, LinHu Economic Zone

Wujiang City, Jiangsu Province, China

Tel: + 86-512-63627980

Fax: + 86-512-63627981

INDEX

<i>Item</i>	<i>Content</i>	<i>Page</i>
1.	天線規格表 1
2.	成品圖 2
3.	測試報告 3~5
4.	Cable 規格 6~7
5.	天線桿套材質特性 8~14
6.	天線固定座材質特性 15~17
7.	Connector 材質特性 18
8.	膠水特性及黏著力測試 19~22

RF Antenna Cable Assembly

Specification



1. Electrical Properties :

- 1.1 Frequency Rang.....2.4GHz ~ 2.5GHz
- 1.2 Impedance 50 Ω Nominal
- 1.3 VSWR 1.92 Max.
- 1.4 Return Loss..... -10dB Maximum
- 1.5 Electrical Wave.....1/2 λ Dipole
- 1.6 Gain..... 1.8 dBi
- 1.7 Admitted Power..... 1W

2. Physical Properties :

- 2.1 Cable.....RG-178 Coaxial Cable
- 2.2 Antenna Body..... TPE
- 2.3 1.Antenna Base..... PC
2.Antenna Base..... PBT
- 2.4 Operating Temp. -20°C ~ +65°C
- 2.5 Storage Temp. -30°C ~ +75°C
- 2.6 Color Gray
- 2.7 ConnectorSMA Straigh Plug Reverse

5		6	
REV.	DATE	DESCRIPTION	

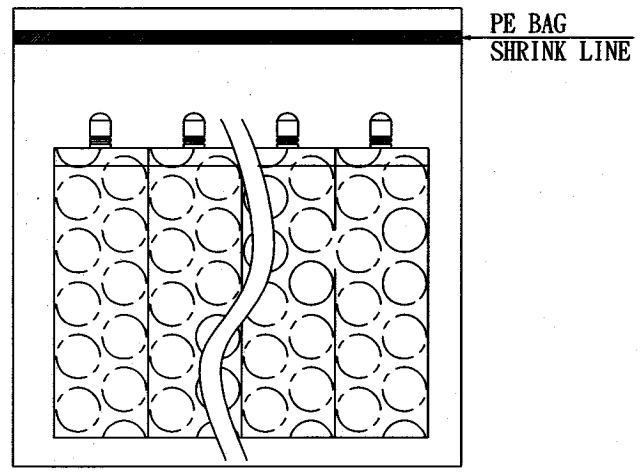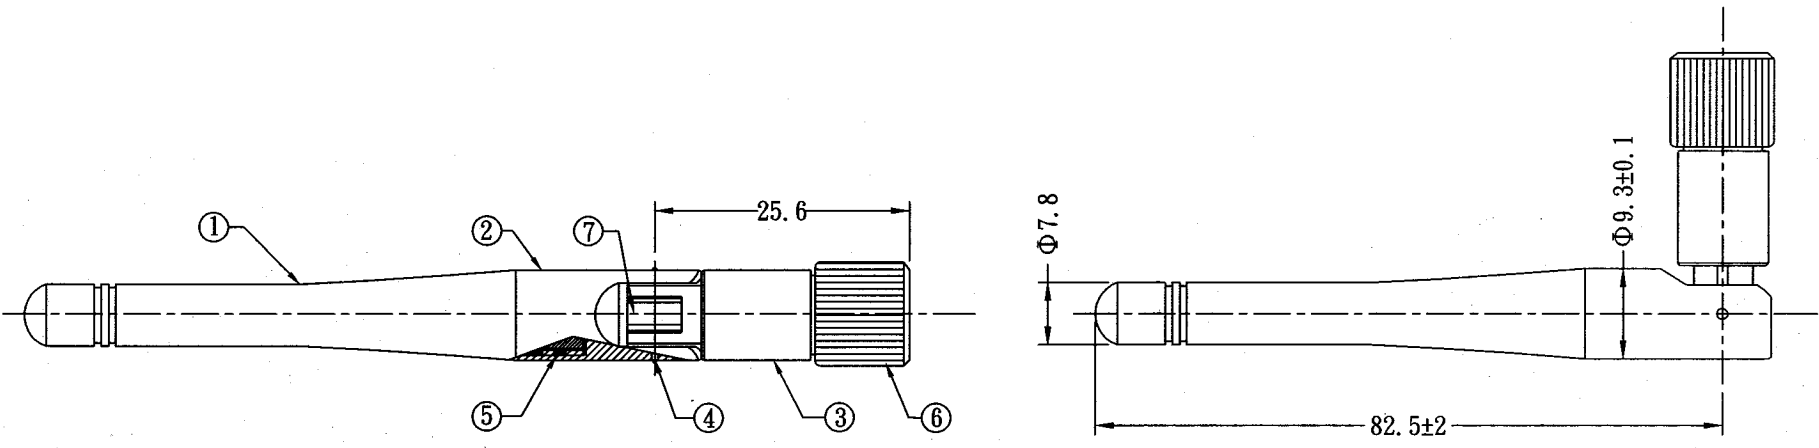

PACKING: 20PCS/BAG

NO.	DESCRIPTION	Q' TY	EQUIVALENT
7	CABLE	RG-178, TRANSLUCENT BROWN, 50Ω.	1 EQUIVALENT
6	CONNECTOR	SMA STRAIGHT PLUG/REVERSE	1 EQUIVALENT
5	GROUND TUBE	BRASS, NI-PLATED	1 EQUIVALENT
4	RIVET	BRASS, PLATING BLACK Zinc	2 EQUIVALENT
3	ANTENNA BASE	PBT, COLOR: BLACK, WY-002	1 EQUIVALENT
2	ANTENNA BASE	PC, COLOR: BLACK, WY-002	1 EQUIVALENT
1	ANTENNA COVER	TPE, COLOR: BLACK, WY-002	1 EQUIVALENT


XX.±3.0	APPROVED	CUSTOMER: 深圳市普聯技術有限公司
X.±2.0	<i>[Signature]</i>	W. Y. P/N: C636-510011-A
.X±1.0	CHECKED	PART NAME: RF ANTENNA ASSEMBLY
.XX±0.5	<i>[Signature]</i>	PART NO.: 31010006
.XXX±0.1	DRAWN	REV. UNIT PAGE FILE: SSR-00193
⊕	<i>[Signature]</i>	B mm 1/1 DATE: 2005.05.18

WHA YU
INDUSTRIAL CO., LTD.
譯裕實業股份有限公司


28 May 2004 09:45:17

CH1 LOG 5 dB/ REF -10 dB
S11 4: -4.1677 dB 2 210.900 000 MHz

CH2 SWR 1 / REF 1
S11 4: 4.2400 2 210.900 000 MHz

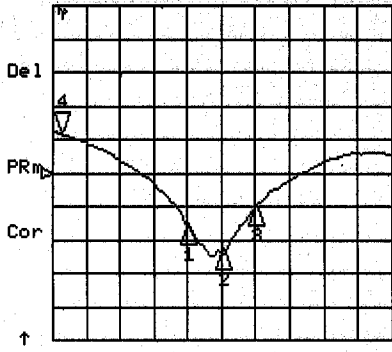

CH1 Markers
 1: -17.704 dB
 2.40000 GHz
 2: -21.502 dB
 2.45000 GHz
 3: -15.028 dB
 2.50000 GHz

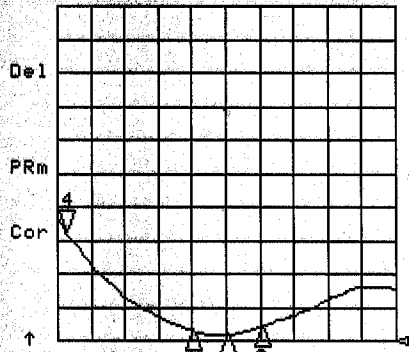


CH2 Markers
 1: 1.2995
 2.40000 GHz
 2: 1.1837
 2.45000 GHz
 3: 1.4309
 2.50000 GHz

START 2200.000 MHz STOP 2700.000 MHz

START 2200.000 MHz STOP 2700.000 MHz

CH3 S11 1 U FS 4: 16.597 Ω -30.745 Ω 2.3414 pF 2 210.900 000 MHz

Del
Cor

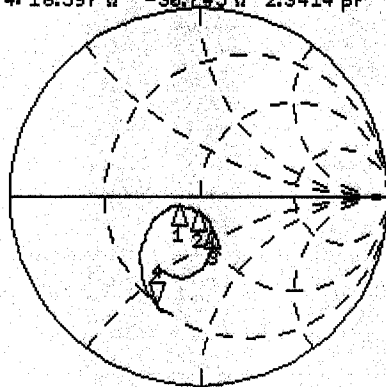

CH3 Markers
 1: 39.111 Ω
 -4.0623 Ω
 2.40000 GHz
 2: 47.465 Ω
 -7.8223 Ω
 2.45000 GHz
 3: 52.891 Ω
 -16.235 Ω
 2.50000 GHz

↑


START 2 200.000 000 MHz

STOP 2 700.000 000 MHz

RF Antenna Assembly


SPEC : 2.4 ~ 2.5GHz

Far-field amplitude of antenna-1-h.nsi

 2.4GHz

 2.45GHz


 2.5GHz

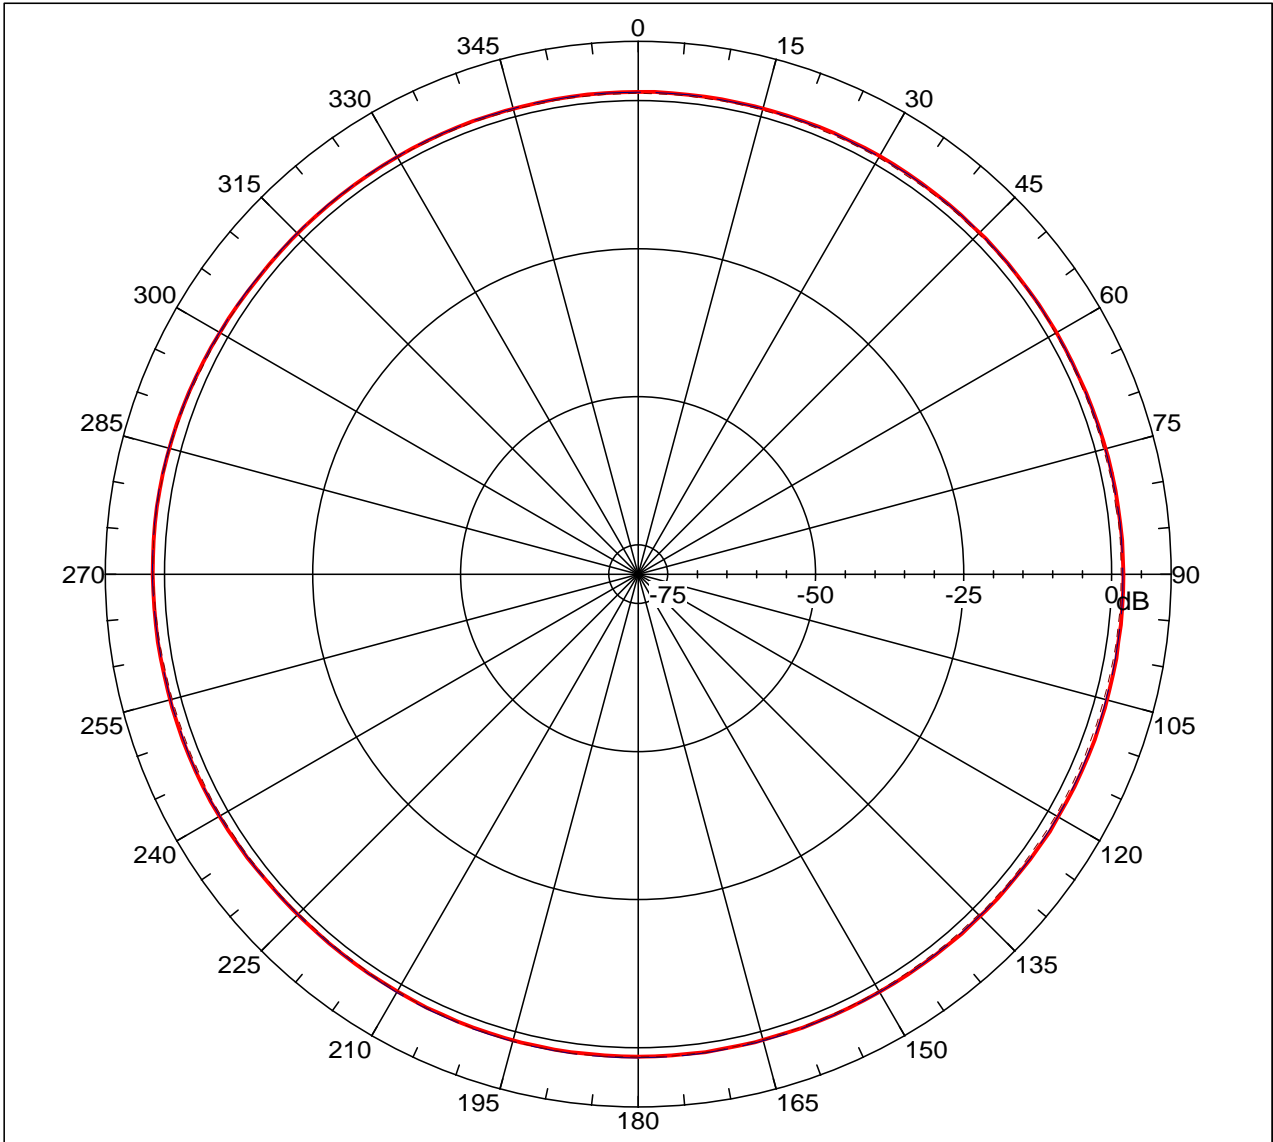

RF Antenna Assembly


SPEC : 2.4 ~ 2.5GHz

Far-field amplitude of antenna-1-e.nsi

 2.4GHz

 2.45GHz

 2.5GHz

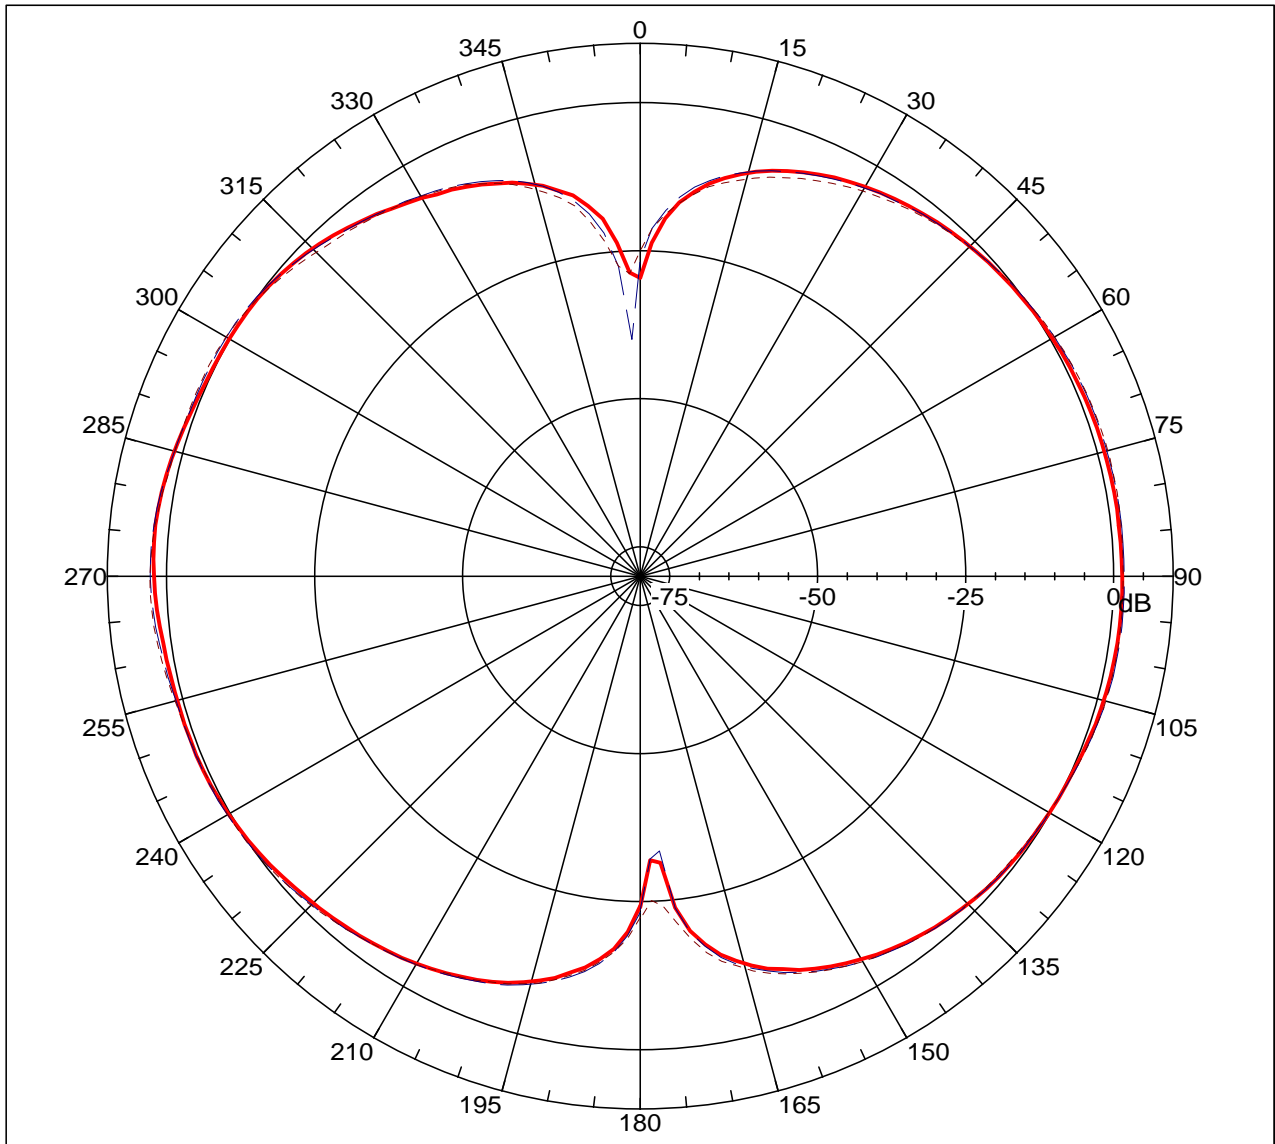


RG 178 B/U	FEP INSULATED HIGH-FREQUENCY COAXIAL CABLE	PAGE	1 / 2
PRODUCT STANDARD		ISSUED	21. Oct. 2003
		REVISED	

I - Scope


This specification presents a FEP insulated high-frequency coaxial cable AWG 30, 1.8 mm O.D. for internal wiring of electronic equipment, such as Computer / Notebook with wireless communication systems.

II - Construction

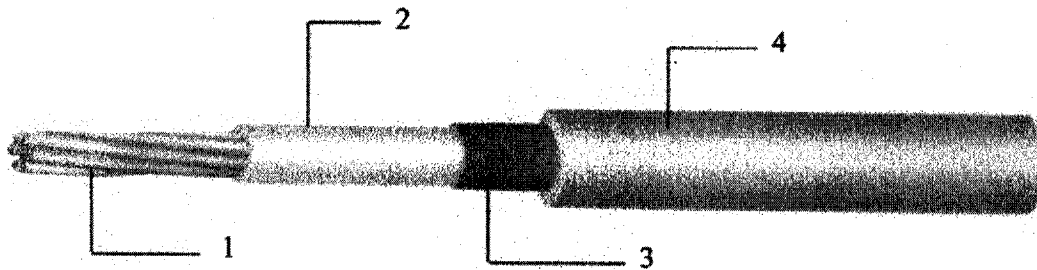

Item		Unit	Details
1. Inner Conductor	Material	—	CP-AG
	Composition	No./mm	AWG 30 or 7 × 0.1
	Dia. (approx.)	mm	0.305
2. Dielectric	Material	—	Extruded FEP
	Nom. O.D.	mm	0.84 ± 0.05
	Color	—	Natural
3. Outer Conductor	Material	—	Silver coated copper
	Composition	—	Braided (16 / 3 / 0.1)
	Dia. (approx.)	mm	1.29 ± 0.07
4. Jacket	Material	—	Extruded FEP
	Dia.	mm	1.80 ± 0.08
	Color	—	Standard color is Light Orange

Note :



MADE BY

APPROVALS


Shen Bin Chao
Shen Bin Chao

RG 178 B/U	FEP INSULATED HIGH-FREQUENCY COAXIAL CABLE	PAGE	2 / 2
PRODUCT STANDARD		ISSUED	21. Oct. 2003
		REVISED	

III – Characteristics

Item	Unit	Specified Value	Note
Temperature Rating	°C	-55 ~ +200	
Voltage Lasting	V	1000	
Dielectric strength	—	Dielectric core: No breakdown at AC 3 kv for 0.2 sec.	Spark test
		Jacket: No breakdown at AC 3 kv for 0.2 sec.	Spark test
Characteristic Impedance	Ω	50 ± 2	TDR method
Capacitance	pF / ft	29.4	
Attenuation. (Max.)	dB/100ft	16.0	100.0 MHz
		33.0	400.0 MHz
		52.0	1.0 GHz
		94.0	3.0 GHz
Approx. Weight	g / m	7.68	

Note :



MADE BY

APPROVALS

Probe Lin
Shen Bin Chao

Arnitel
polyether esters
polyetherester
esters de polyether

天線桿套材質特性表



Units Einheiten Unites	EM400	EM460	EL550	EL630	EL740	PL380
	1.12	1.16	1.20	1.23	1.27	1.18
°C	195	185	202	212	221	197
μm/m.k	220	160	180	140	110	150
°C	\	\	110	115	120	\
°C	130	150	180	200	200	145
°C	\	50	85	115	150	\
%	0.30	0.30	0.20	0.20	0.15	0.40
%	0.75	0.70	0.55	0.60	0.90	7.0
*	HB	HB	HB	HB	HB	HB
Mpa	55	110	220	375	900	60
Mpa	4.0	7.1	13.2	20.2	26.9	3.5
Mpa	5.4	9.0	15.7	23	22.6	5.2
Mpa	8.4	11.4	16.6	22.0	26.3	8.5
Mpa	17	21	32	40	45	16
%	700	800	600	600	360	450
kJ/m ²	NB	NB	NB	NB	NB	NB
kJ/m ²	NB	NB	NB	NB	200	NB
kJ/m ²	NB	NB	NB	NB	9	NB
kJ/m ²	NB	NB	20	4	4	NB
	38	45	55	63	74	38
MV/m	\	\	\	\	\	\
Ω.cm	5*10 ¹⁴	10 ¹⁴	10 ¹⁴	10 ¹⁴	10 ¹²	10 ¹²
Ω	>10 ¹³	>10 ¹⁴	>10 ¹⁴	>10 ¹⁴	>10 ¹⁰	>10 ¹³
\	4.1	\	\	3.8	\	4.7
\	4.0	4.4	4.0	3.4	3.3	4.4
x10 ¹⁴	10	\	\	3.8	\	310
x10 ¹⁴	170	350	400	350	300	350
\	800	800	600	600	600	800
\	600	600	600	800	800	600

Arnitel

2.2 Product coding

The structure of the Arnitel productcodes is illustrated with the following example:

U M 55 1 - V

Thermoplastic elastomer type:

- E = polyether ester; polyether = PTHF
- P = polyether ester; polyether = PEO/PPO
- U = polyester ester; (with extra urethane linkages)

Indication of viscosity range or processing technique

- L, M = injection moulding and extrusion
- B = blow moulding grade

Indication of hardness (Shore D)

Serial number

Indication of additives, performance

- H = heat-stabilized
- L = light/UV stabilized
- V = flame-retardant (not V-0)
- S = flame-retardant (V-0)

Figure 2.2: Arnitel product coding

2.3 Product portfolio

The Arnitel productrange is available with a hardness from 38 to 74 Shore D. The general Arnitel grades are shown in table 2.2. In order to enhance the flexibility of the portfolio a set of masterbatches (a.o. for heat, UV, etc) are on offer (refer to § 2.4).

Because of the development of these masterbatches heat stabilised Arnitel P is suggested for application areas where thermo-oxidative stability is an issue. For applications where colour and UV stability is required, the Arnitel E range is advised.

	Shore D					
	38	40	46	55	63	74
Arnitel E		EM400	EM460	EL550 EM550	EL630 EM630	EL740 EM740
Arnitel P	PL380		PL460	PL580 PM581		
Arnitel U				UM551 UM551-V UM552 UM552-V	UM622	

Table 2.2: Arnitel productrange for general purpose

Besides these multi-purpose grades, specialty grades can be offered for specific purposes and/or application areas. These grades are not intended for regular sales and are therefore restricted. Permission from marketing is needed before sampling is initiated.

	Arnitel E	Arnitel P	Arnitel U
Automotive			
• CVJ boots	EB460 EB463 EB464		
• Boyplugs		PL380-M0	
Extrusion			
• Roofing foil	EM402-L		

Table 2.3: Examples of specialty grades

Amitel® EL630/EM630

2.8.31 General:

Amitel is the brand name of a series polyester based thermoplastic elastomers. These polymers combine excellent processability with good elastomeric properties between -40 and 200°C. Amitel EL630 and EM630 are excellent materials for injection moulding and extrusion applications respectively. The chemical structure of Amitel EL630/EM630 is shown below.

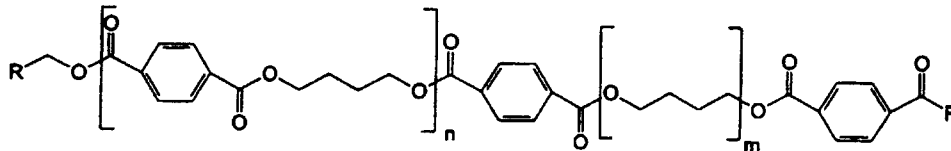


Figure 2.9: Chemical structure of Amitel EL630/EM630.

Another way of writing the structure of Amitels is shown below in Figure 2.




Figure 2.10: Simplified structure of Amitel EL630/EM630 .

Amitel EL630/EM630 is TOSCA registered (including DSL-Canada) under CAS 37282-12-5

2.8.32 Thermal properties:

• **Modulus-temperature behaviour:**

The materials have a glass transition at circa -40°C and a typical melting point at 213°C. The modulus-temperature behaviour is shown in graph 2.76, for comparison, accompanied by other Amitel E types.

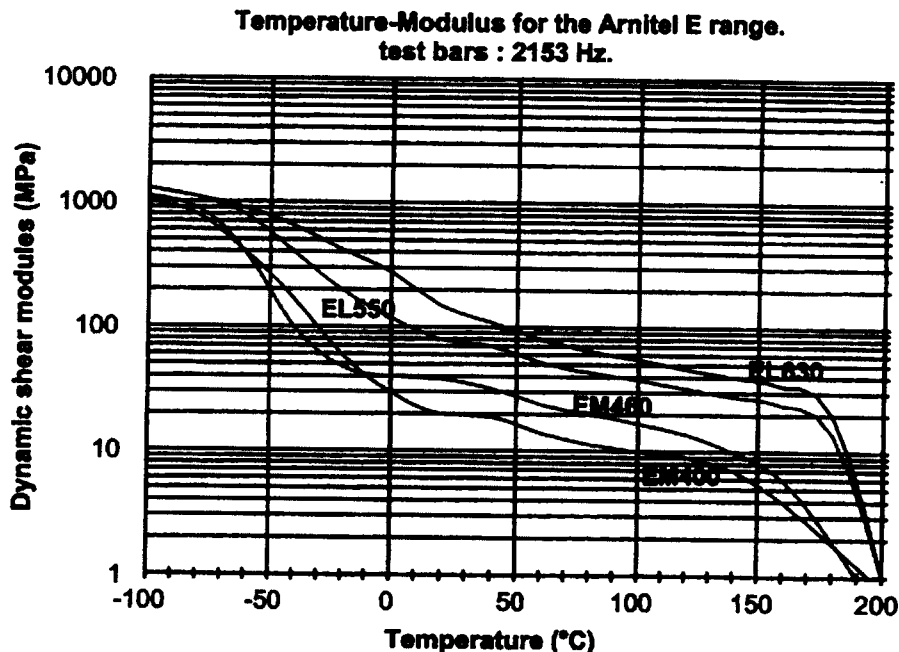

Graph 2.76: Modulus-temperature behaviour of Amitel EL630/EM630.

Arnitel® EL630/EM630

Although information on performance at higher temperatures may be extracted from the above shown graph, a Vicat or HDT are shown in table 2.29.

analysis	SI unit	typical data	test method
Vicat A	(°C)	200	ISO 306/A
Vicat B	(°C)	125	ISO 306/B
HDT-B	(°C)	115	ISO 75-1

Table 2.29: Vicat and HDT data on Arnitel® EL630 and EM630


Arnitel EL630 and EM630 have a melting point of 213°C as found in the second heating curve of a DSC. The polymer will crystallize at 155°C using a 20°C/min cooling rate. The thermal expansion coefficient of Arnitel EL630/EM630 and is $140 \cdot 10^{-4} \mu\text{m/m.K}$.

• **Heat aging:**

Arnitel EL630/EM630 shows an optimum between heat resistance and colour stability. Heat aging for EL630/EM630 is under test at this moment, however the data will be between EL550 and EL740. Arrhenius curves of thermo-oxidative heat aging are shown in graph 2.77. Criterium chosen is retention of 50% original elongation at break.

Heat aging of Arnitel E40D, 46D, 55D and 74D.

Natural products, Arrhenius plot.

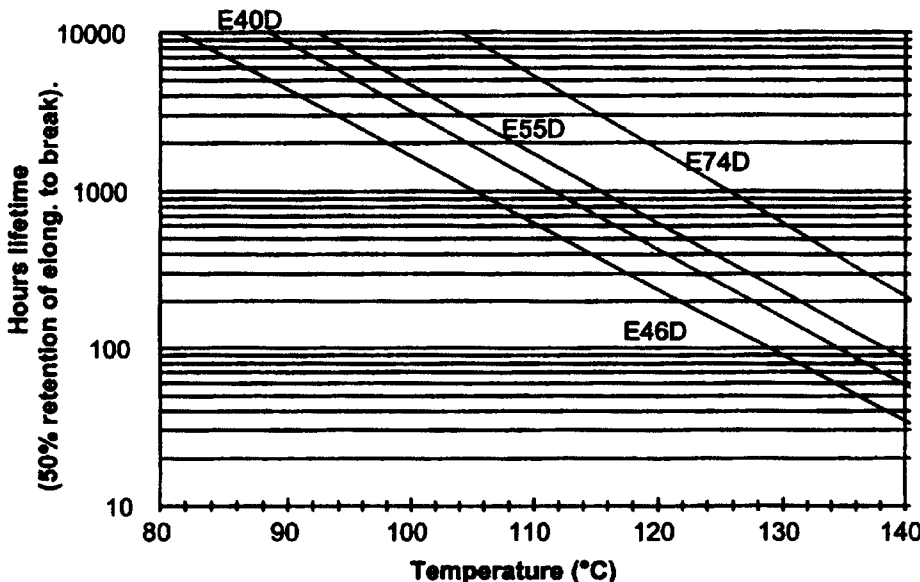

Graph 2.77: Heat stability for Arnitel E-range.

Heat ageing can be improve using a stabilisation masterbatch, however for heat stabilisation the P-range is preferred for it's excellence in performance. These data can be found in the Arnitel properties summary or an Arnitel P datasheet.

2.8.33 Processing and Handling:

Arnitel EL630/EM630 is a polyester with a density of 1.12 g/cm^3 according ISO 1183. Due to the polyester nature of these materials it is of major importance to store the material dry prior to processing. Materials packaged in sealed packaging should have a moisture content lower then 500 ppm. The polymer will contain 0.12% moisture in 50% RH and 0.58% water after saturation in water. Both numbers are in equilibrium. If samples have become wet during storage a drying step of 24 hours 120°C (or 6 hours 140°C) prior to use will prevent degradation of the material during processing combined with an eventual loss of properties. The air or nitrogen will have to have a dew point of at least -30°C .

Arnitel® EL630/EM630

• **Processing:**

Arnitel EL630/EM630 shows a single melting point at 195°C in DSC. Processing conditions are shown in the table below.

polymer	zone 1	zone 2	zone 3	additional	melt	mold
EL630	225	230	235	235	225-235	20-50
EM630	225	230	235	235	235	50


All temperatures are in °C.

Table 2.30: Processing conditions for Arnitel EL630 and Arnitel EM630.

• **Rheology:**


The temperature depending melt viscosity of Arnitel EL630/EM630 and are shown below in graph 2.80 and 2.81 respectively.

**Shear rate dependent of the melt viscosity of Arnitel EL630.
Effect of melt temperature.**

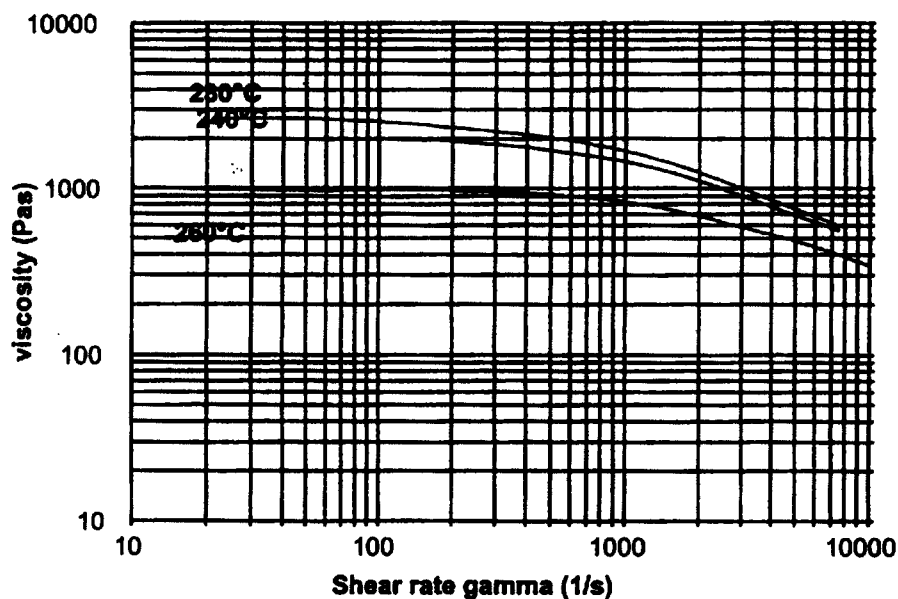

Amitel[®] EL630/EM630

Capillar melt viscosity of Amitel EM630.
240, 250 and 260°C.

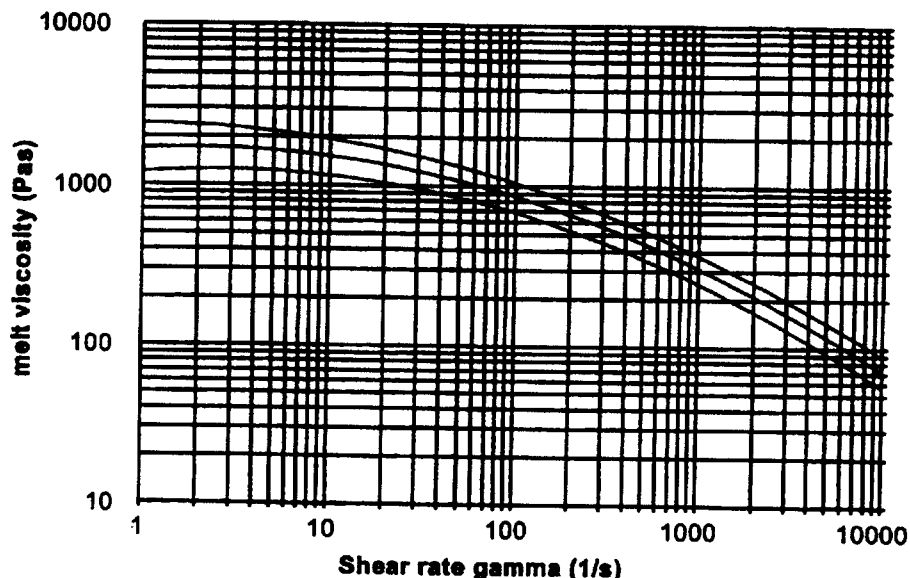

Graph 2.80 and 2.81: Temperature dependancy of the melt viscosity for Amitel EL630 and EM630 .

The MFI values are shown in table 2.31.

		EL630	EM630	
MFI 230°C	g/10 min		7	ISO 1133
MFI 240°C	g/10 min	30		ISO 1133

Table 2.31: MFI for Amitel EL630/EM630.

• **Use of regrind:**

Amitel can readily be recycled. If the MFI of the regrind is up or down to four points higher, 20% can be recycled. A difference of 2 MFI points allows up to 50% of regrind. Obviously the regrind should be dried properly before use.

2.8.34 Mechanical properties:

If Amitel EL630 or Amitel EM630 are processed properly the materials will have mechanical properties as shown in table 2.32.

Mechanical property	SI Unit	typical data*		test method
		EL630	EM630	
Hardness	Shore D	63	63	ISO 868
Tensile modulus (1 mm/min)	MPa	330	330	ISO 527
Tensile strength (50 mm/min)	MPa	30	30	ISO 527
Strain at break	%	350	350	ISO 527
Tensile stress at 5% strain	Mpa	11.5	11.5	
Tensile stress at 10% strain	Mpa	15.9	15.9	
Tensile stress at 50% strain	Mpa	17.3	17.3	
Tear strength Graves	KN/m	145	145	DIN53515
Izod notched 23°C (73°F)	KJ/m ²	NB	NB	ISO 180/1A
Izod notched -30°C (-22°F)	KJ/m ²	4	4	ISO 180/1A
Charpy notched 23°C (73°F)	KJ/m ²	NB	NB	ISO 179/1eA
Charpy notched -30°C (-22°F)	KJ/m ²	12	12	ISO 179/1eA

Data for dry natural materials.

NB: No Break

Table 2.32: mechanical properties of Amitel[®] EL630.

Arnitel® EL630/EM630

• **Abrasion:**

Arnitels show good abrasion resistance in both Taber and DIN 53516 abrasion tests. Data are shown in the Arnitel general property overview (also included in the EPIC)

2.8.35 Flame retardancy:

Arnitel EL630 and EM630 show in an ISO1210/A flammability test a burning rate leading to a classification FH-1. Flame retardancy can be improved using a halogenated or halogen free FR masterbatch.

2.8.36 Electrical properties:

Arnitel EL630/EM630 can be used for cable jacketing applications. If the material is in permanent contact with copper a copper stabilisation package should be added. If the copper wires are coated with a tin layer, no stabilisation is necessary. The electrical properties are shown in table 33.

Electrical property	SI Unit	typical data*		test method
		EL630	EM630	
Dielectric strength	KV/mm	22	22	IEC 243-1
Relative permittivity (ϵ_r) at 1 kHz	-	4.4	4.4	IEC 250
Dissipation factor ($\tan \delta$) at 1kHz	-	0.019	0.019	IEC 250
Comparative tracking index	-	600	600	IEC 112
Volume resistivity	$10^{14} \Omega \cdot \text{cm}$	1	1	IEC 93
Surface resistivity	$10^{14} \Omega$	1	1	IEC 93

Table 2.33: Typical electrical properties of Arnitel® EL630 and EM630.

2.8.37 Chemical resistance:

Arnitel EL630 and EM630 are sensitive to strong bases and strong acids, especially at elevated temperatures. In some halogenated hydrocarbons (like tetrachloroethane), the materials (partially) dissolve. For a full review on chemical resistance of Arnitel EL630 and EM630 request the chemical resistance brochure.

• **Hydrolysis**

Like all polyesters Arnitel are sensitive to moisture, however Arnitels are more stable to water than e.g. PET and PBT. graph 2.84 shows the hydrolytic stability of Arnitel EL630 at 100°C and in steam (120°C). For improved hydrolysis stability, using a polycarbodiimid containing masterbatch like Stabaxol® in an option. To maintain all other properties use a masterbatch based on polyester. Data on the Stabaxol stabilised grade are shown in graph 2.85.

■ Panlite L-1250Z

Category	Unit	Test Method	Condition	L-1250Z 100
Melt volume flow rate	cm ³ /10min	ISO 1133	300°C load 1.2kg	8
Density	kg/m ³	ISO 1183	—	1200
Water absorption rate	%	ISO 62	in water 23°C24h	0.2
Light transmission	%	ASTM D 1003	thickness 3mm	88
Refractive index	—	ASTM D 542	—	1.585
Tensile modulus	MPa	ISO 527-1 and ISO 527-2	1mm/min	2400
Tensile stress at yield	MPa		50mm/min	61
Tensile strain at yield	%		50mm/min	6
Nominal tensile strain at break	%		50mm/min	>50
Flexural modulus	MPa	ISO 178	2mm/min	2350
Flexural strength	MPa		2mm/min	93
Charpy impact strength	KJ/m ²	ISO 179	unnotched	NB
			notched	76
Heat deflection temperature	°C	ISO 75-1 and ISO 75-2	1.80MPa	129
			0.45MPa	142
Vicat softening temperature	°C	ISO 306	50°C/h 50N	149
Mold shrinkage	%	In-house method	parallel	0.5~0.7
			vertical	0.5~0.7
Coefficient of linear expansion	× 10 ⁻⁴ /°C	ISO 11359-2	parallel	0.7
			vertical	0.7
Specific inductive capacity	—	IEC 60250	100Hz	3.1
	—		1MHz	3
Dielectric loss tangent	× 10 ⁻⁴	IEC 60250	100Hz	10
	× 10 ⁻⁴		1MHz	90
Volume resistivity	Ω·m	IEC 60093	—	>1 × 10 ¹³
Surface resistivity	Ω	IEC 60093	—	>1 × 10 ¹⁵
Withstand voltage	MV/m	IEC 60243-1	short time test	30
Tracking resistance	—	IEC 60112	—	250
Flammability	—	UL 94	—	V-2(0.40mm) HB(1.5mm)
Temperature index	°C	UL 746B	electric 1.47mmt	125
			impact 1.47mmt	115
			non-impact 1.47mmt	125

※The values listed are specification values, not certified values.

■ Molding

1. Predrying

The water content of Parlite is about 0.2% at room temperature. In order to obtain good molding results, reduce the product moisture content to 0.02% or below. This will also avoid problems with deterioration in physical properties, foaming and silver streaking caused by hydrolysis.

Predrying conditions

Type of drying machine	Box type hot blast drying machine	Hopper dryer
Drying temperature	120°C	120°C
Drying time	5 hours or more	5 hours or more
Remark	The thickness of pellet layer should be 3 cm or less. The hopper of the molding machine should be heated to maintain the pellet temperature between 100°C and 120°C, and to avoid moisture absorption.	For continuous molding, use a machine with a continuous molding capacity of 5 hours or more. If a dehumidifying type machine is used, more efficient drying will be performed.

■ Injection Molding

Table of Standard injection conditions


Predrying		120°C × 5 hours or more. Ensure thorough drying to reduce the moisture content to 0.02% or below.
Injection Molding machine		Select a molding machine with a shot capacity of 1.5–3 times as that of the weight of the molded product.
Molding Condition	Molding Temperature	270–320°C
	Mold Temperature	80–120°C
	Screw Revolution	40–100rpm
	Injection Speed	medium–high
	Injection Pressure	98.1MPa–147.1MPa
	Back Pressure	10MPa or less

Valox 物性 Typical Properties of Valox

PBT

Valox®

項目 Property	試驗法 ASTM Test Method	單位 Units	300				400						500			700				
			310	310SEO	325		DR51	420		414	457	DR48	420SEO	507	508	553	735	745	750	780
比重 Specific Gravity	D792 23 C		1.31	1.41	1.31		1.40	1.53		1.60	1.45	1.50	1.62	1.51	1.49	1.60	1.62	1.46	1.75	1.77
吸水率 Water Absorption	D570 23 C 24HRS	%	0.08	0.08	0.08		0.07	0.06		0.06	0.07	0.07	0.07	0.06	0.07	0.08	0.08	0.09	0.07	0.02
成形收縮率 Mold Shrinkage	D955	%	1.7~2.3	1.0~1.7	1.7~2.3		0.3~0.5 0.8~1.0	0.1~0.3 0.7~0.9		0.1~0.2 0.6~0.8	0.5~0.7 0.8~1.2	0.3~0.5 0.8~1.0	0.1~0.3 0.7~0.9	0.1~0.2 0.3~0.6	0.1~0.2 0.3~0.6	0.1~0.2 0.3~0.6	0.2~0.5 0.4~0.9	1.0~1.4 1.0~1.4	0.3~0.5 0.5~0.7	0.3~0.4 0.4~0.6
伸張強度 (絕伏點) Tensile Strength	D638 23 C	kg/cm ²	530	600	530		910	1,200		1,300	790	910	1,200	1,200	1,200	1,200	900	500	900	980
		MPa	52.0	58.8	52.0		89.2	117.7		127.5	77.5	89.2	117.7	117.7	117.7	117.7	88.3	49.0	88.3	96.1
伸張斷裂 (斷點點) Tensile Elongation	D638 23 C	%	300	80	300		5	3		3	5	5	3	5	5	5	3	30	3	
彎性強度 Flexural Strength	D790 23 C	kg/cm ²	840	1,000	840		1,400	1,930		2,100	1,260	1,400	1,900	1,900	1,800	1,800	1,500	910	1,400	1,680
		MPa	82.4	98.1	82.4		137.3	189.3		205.9	123.6	137.3	186.3	186.3	176.5	176.5	147.1	89.2	137.3	164.8
彎性模數 Flexural Modulus	D790 23 C	$\times 10^3$ kg/cm ²	24	26	24		45.8	77		90	35	50	80	75	75	75	90	35	84	105
		MPa	2,350	2,550	2,350		4,490	7,550		8,830	3,430	4,900	7,850	7,350	7,350	7,350	8,830	3,430	8,240	10,300
IZOD 衝擊強度 Izod Impact Strength	D256 23 C	kg cm/cm	6	5	6		7	10		12	6	5.5	10	10	14	8	8	10	6	6
		J/m	59	49	59		69	98		118	59	54	98	98	137	78	78	98	59	59
洛氏硬度 Rockwell Hardness	D785		R117	R120	R117		R118	R118		R117	R118	R118	R119	R119		R118	R110	R112	R114	R116
磨損消耗 Taber Abrasion Resistance	D1044	mg																		
變形溫度 Deflection Temperature Under Load	D648 (0.455MPa)	°C	154	163	154		210	215		216	214	210	215	216		210	220	165	204	210
		D648 (1.820MPa)	°C	55	71	55		190	208		207	160	182	205	200	190	171	200	88	194
線形係數 Coefficient of linear therm	TMA 法 -30 C~30 C	$\times 10^{-5}$ mm/m/°C [$\times 10^{-5}$ K]	13	9	13		5	3		3	9	4	3	3		3	4	8	3	2.5
耐燃性 Flammability	UL94		HB(1.47)	V-0(0.71)	HB(1.47)		HB(1.47)	HB(0.71)		HB相當	V-0(0.71)	V-0(0.71)	V-0(0.71)	HB(0.83)	HB(1.47)	V-0(0.86)	HB(0.81)	HB(1.57)	V-0(0.71)	V-0(0.81)
氧氣指數 Oxygen Index	D2863	%	20	29	20		20	20			30	30	32			32				
VICAT 軟化點 (0.1mm針) Vicat Softening Temperature	D1525	°C	165	165	155		210	215			205	210	215			210				210
UL 認用溫度 UL Recognition Temperature Index		°C		120	120		120	140			120	120	130	125	125	125	140	105	130	130
介電強度 Dielectric Breakdown Strength	D149(1/8")	KV/mm					28	26		29	29	29	30	30		26	43	25	27	26
體積電阻率 Volume Resistivity	D256	$\Omega \cdot \text{cm}$					10^{14}	10^{14}		10^{14}	10^{14}	10^{14}	10^{14}	10^{14}		10^{14}	10^{14}	10^{14}	10^{14}	10^{14}
介電常數 Dielectric Constant	D150 23 C 60Hz						3.6	3.8		3.6	3.3	3.6	3.8	3.7		3.6	4.0	3.3	3.7	3.9
介電損耗 Dielectric Dissipation Factor	D150 23 C 60Hz						0.002	0.002		0.002	0.002	0.002	0.002	0.002		0.002	0.006	0.002	0.006	0.007
耐熱性 Air Resistance	D495	sec	129		184		129	146		85	28	35	60	75		94	100	127	125	126

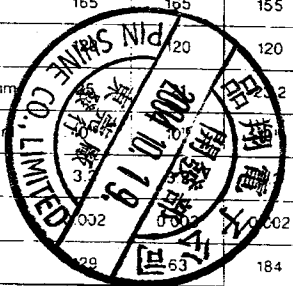

Note: Figures in () of the Table of characteristics are of SI units and those of () are wall thickness. 註: 括弧中之數字為壁厚。

RF SMA Connector

Specification

1. Electrical Properties :


- 1.1 Frequency Rang.....1~3GHz
- 1.2 Impedance 50 Ω Nominal
- 1.3 VSWR1.3 Max.
- 1.4 Voltage rating AC 500V
- 1.5 Withstanding Voltage AC 1000V one minute
- 1.6 Insulation Resistance5000M Ω

2. Mechanical Properties :

- 2.1 Mating / unmating force .. 2 inch-lb
- 2.2 Mating Torque 7~10 inch-lb
- 2.3 Contact Retention4 lbs min. axial force
- 2.4 Cable Retention 15lb for RG316 ; 9lb for RG178
- 2.5 Durability 500 cycles Minimum**

3. Environment Properties :

- 3.1 Temperature Range..... -40 $^{\circ}$ C ~ +85 $^{\circ}$ C
- 3.2 Thermal Shock.....MIL-STD-202, Method 107, Condition B
- 3.3 Shock.....MIL-STD-202, Method 213, Condition I
- 3.2 Vibration MIL-std-202 Method 204, Test Condition D

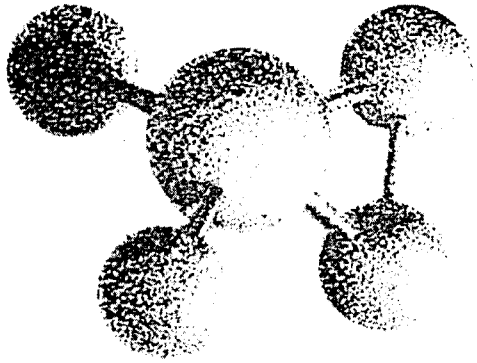

施敏打硬 CEMEDINE 1500

〔一般性質〕

	主 劑	硬 化 劑
主要成分	環氧 (Epoxy) 樹脂	聚醯胺 (Poly-Amido) 樹脂
顏色常態	中間體淺黃色透明液體	色透明液體
不揮發率 (%)	99.6	99.4
黏度(9/20°C)	350	600
比重(20/20°C)	1.16	0.97
溶 劑	無	
硬化劑混合比例phr	60~110	
保持粘度時間	參照混合硬化劑後的粘度變化表	
膠 化 時 間	3小時	
硬化所需時間	6小時10分鐘	
可保存時間(20°C)	2年	

〔特性〕

由兩種液體混合而成的環氧 (Epoxy) 樹脂系黏着劑，能在常溫下硬化，應用範圍至為廣泛，可穩定黏着金屬，塑膠以及其他各種物質，而由於此黏着劑，通常以聚醯胺 (Poly-Amido) 樹脂為其硬化劑，具有下列各優點：

1. 能在常溫下硬化。
2. 縱使所使用的硬化劑份量不同，也不影響其特性。
3. 由於能產生比一般黏着劑富有彎曲性的黏着層，縱使黏着不同材質的物品，也能以黏着層緩和熱膨脹的差別所引起的兩物品彎曲，對機械學的衝擊也能顯示較為良好的性能。
4. 由於能形成透明的黏着層，可以黏着透明的物質，如玻璃等等。

〔用 途〕

由於能強力黏着各種物質，諸如金屬，熱硬化塑膠，玻璃，飛機裝配以及一般家庭器具等等，應用範圍至為廣泛，縱然是複聚乙稀 (Polythylene)，聚酯 (Polyester)，天然以及人造橡膠等，以一般的黏着根本無法黏着的物質，如果加以適當的表面處理，即可強力黏着。

〔實 例〕

汽車、火車、船隻、飛機……（將金屬把手黏着於玻璃窗／可以黏着鋁製品，三聚黑胺 (Melamine) 裝飾板等，於內部以增加強度／不同金屬間為兼防止電傷且黏之／當作防腐塗料亦可）。

電器製品……（由於是一種優秀的黏着劑，使用於高級擴音器、音響線圈的黏着／電磁器或外殼的黏着／線圈框的黏着／鐵粉芯的黏着／馬達線圈的黏着等等）。

建築……（玻璃、壓克力門或將文字板黏於屏風黏住把手／照明設備以及其他塑膠裝飾品的加黏以及組立／不銹鋼製品、鋁製建材、陶器或大理石等需要強力黏劑物品的加黏

高級裝飾品，玻璃以及塑膠製工藝品，精密機械……（照像機，調整距離儀／分光儀等等的固定），其他諸如罐頭，運動器材，公路標誌等等的加黏。除上述各種加黏外，也可以使用作填充劑，鑄模用，敷醫用以及鑄裏用。

加 熱 溫 度	加 熱 時 間
50 °C	120分鐘以上
80 °C	60-90分
100 °C	40-60分
120 °C	30-40分

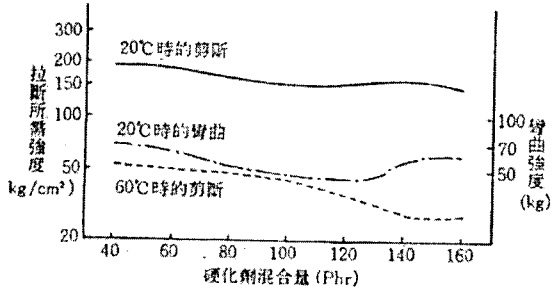


圖 II 2.1
硬化劑混合量和黏力強度
(在20°C七天的硬化)
試驗片：軟鋼板 (25×100×1.6mm)
(Over-lap)12.5mm

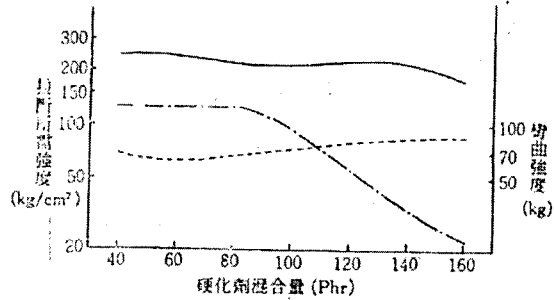


圖 II 2.2
硬化劑混合量和黏力強度
(在80°C一小時的硬化)
試驗片：以及其他同圖 II 2.1

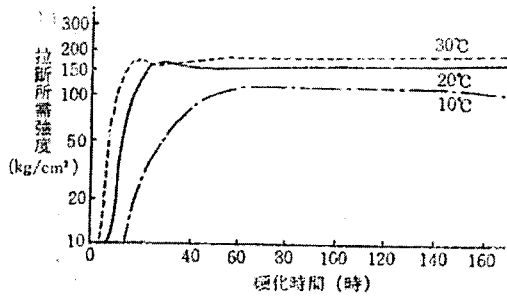


圖 II 2.3
常溫時的硬化特性 硬化劑混合率 100phr

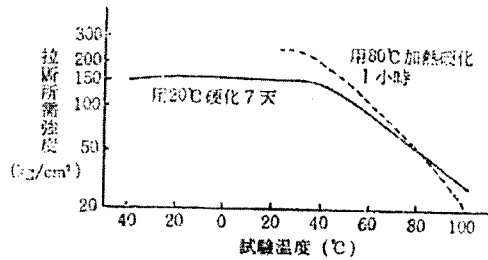


圖 II 2.5
耐熱特性 硬化劑混合率為 100phr

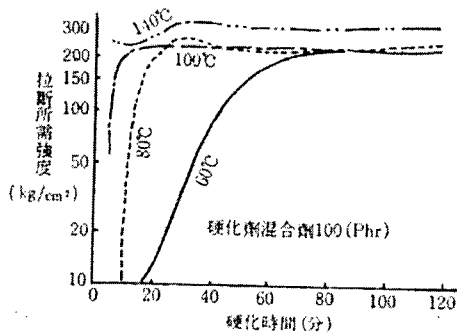


圖 II 2.4
加熱硬化特性 硬化劑混合率為 100phr

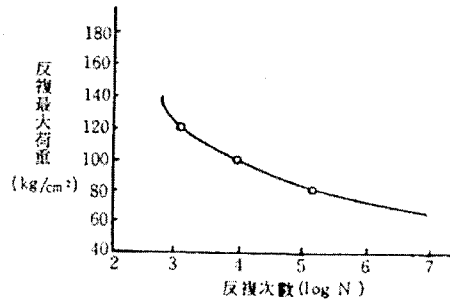


圖 II 2.6
老化特性

表 II 2.1 物理特性

抗張力 (kg/mm ²)	5.04	硬度 {	68
抗折力 (kg/mm ²)	7.40	{	67
彎曲彈性率 (kg/mm ²)	214	{	82
衝擊強度 (kg/mm ²)	11.6	表面固定電阻 (Ω)	5.6×10 ¹³
壓縮強度 (kg/mm ²)	15.10(6.41) ⁽¹⁾	體積固有電阻 (Ω-Cm)	10.5×10 ¹³
熱變形溫度 (°C)	47	誘電率 (10 ⁶ cycle)	2.94
		電壓破壞 (kv/mm)	19

表II 2.2 拉斷所需強度

被 粘 體	拉 斷 所 需 強 度	被 粘 體	拉 斷 所 需 強 度 (20°C)
樟 樹 材	83	多 元 焦 炭	22
馬 來 西 亞 杉 材	106 *	苯 乙 烯 樹 脂	19
針 葉 樹 材	99 < *	壓 克 力 樹 脂	30
杉 材	66	硬 質 鹽 烯 樹 脂	36
鐵	158	三 聚 氰 胺 裝 飾 板 (表 面)	55
鋁	61	三 聚 氰 胺 裝 飾 板 (背 面)	45
黃 銅	60	F R P	125
銅	80		
鍍 電 鍍	71		
銑 電 鍍	50		

[註] 1. 粘着條件: 20°C, 硬化7天, 硬化劑混合比 100phr(接合部over-lap)12.5mm。

2. *記號者表示材料拉斷。

表II 2.3 促進劣化特性

試 驗	未試驗前的粘力強度 (kg/cm ²)	比較調整試驗片的粘力強度(1) (1個月) (kg/cm ²)	經過各試驗1個月後的粘力強度 (kg/cm ²)	經過各試驗1,000小時後的粘力強度 (kg/cm ²)
利用測候儀所做的耐候試驗	143	150	—	166
利用噴射鹽水的促進試驗	143	150	100	—
利用高溫高濕的促進試驗(2)	143	150	143	—
利用反復冷卻的促進試驗(3)	143	150	183	—

[註] (1) 20±1°C, 65±5%RH 各保持1個月的試驗片; (2) 50°C100%RH; (3) -5°C8小時~50°C16小時。

表II 2.4 耐 候 性

		暴露前的粘力強度		拉斷所需強度 (kg/cm ²)
				147
比較調整試驗片的粘力強度 (6個月) ※	※	156	在戶外暴露6個月的粘力強度	147
" (1年) ※	※	138	" 1年 "	152
" (2年) ※	※	130	" 2年 "	138
" (3年) ※	※	123	" 3年 "	137
" (10年) ※	※	111	" 10年 "	130

[註] ※20±1°C, 65±5%RH 保持各期間的試驗片。

表II 2.5 耐水性 (20°C, 7天硬化)

試驗	拉斷所需強度 (kg/cm ²)				
	時間	0	3個月	6個月	1年
常態試驗		120	106	123	120
耐水試驗			109	117	109

[註] 硬化劑混合比為 100phr
試驗片: 不銹鋼 (100×25×1.5mm)
(接合部Over-lap)12.5mm。

表II 2.6 耐水性 (60°C, 2小時硬化)

試驗	拉斷所需強度 (kg/cm ²)				
	時間	0	3個月	6個月	1年
常態試驗		157	150	169	163
耐水試驗			133	108	116

[註] 同表II 2.5

表II 2.7 耐油性

拉斷所需強度 (kg/cm²)

放置日數	1天	3天	5天	10天	20天	1個月
放置於20°C室溫	—	—	—	80.0	—	79.0
0°C油中	—	—	77.5	87.5	—	80.0
20°C油中	—	—	82.5	77.6	—	89.5
70°C油中	77.6	75.3	80.0	74.3	—	71.0
循環油中 cycle	—	—	79.0	78.0	89.0	76.0

放置日數	40天	2個月	3個月	6個月	1年	10年
放置於 20°C室溫	—	—	73.0	65.9	76.3	75.9
0°C油中	—	86.5	71.5	80.5	80.2	—
20°C油中	—	70.5	79.5	78.7	79.7	—
70°C油中	—	75.5	—	75.4	68.3	—
循環油中 (cycle)	71.5	—	—	—	—	—

[註] 1. 硬化劑混合比為80phr，試驗片電木片(100×25×3mm)接合部(Over-lap)12.5mm 2. 油為變壓器油。
3. 試驗片全部破裂。

表II 2.8 耐溶劑、耐藥品性

種類	浸漬7天後的黏力保持率(%)		浸漬1個月後的黏力保持率(%)			
	以20°C硬化7天的試驗片	以80°C硬化1小時的試驗片	以20°C硬化7天的試驗片	以80°C硬化1小時的試驗片		
溶劑	乙醇	107.0	80.6	94.1	78.8	
		85.5	63.8	51.7	66.8	
		88.8	69.5	93.4	70.8	
		89.5	71.3	97.4	68.7	
		90.2	64.7	101.3	69.1	
油	植物油	102.7	90.8	107.3	90.3	
		96.2	87.8	98.1	84.2	
藥品	蒸餾水	93.4	72.3	96.3	69.3	
		10% 硝酸溶液	93.4	72.8	79.8	69.8
		10% 硫酸溶液	74.7	67.8	70.8	57.2
		10% 苛性蘇打溶液	97.2	74.3	83.8	74.3
		10% 食鹽水溶液	89.6	71.8	91.0	69.8
	10% 醋酸溶液	94.2	77.8	78.4	64.2	

[註] 黏劑混合率=1:1，試驗片：軟鋼片(25×100×1.6mm)但是耐藥試驗時使用了SUS-27，接合部(Over-lap)為12.5mm。

容量規格 = (主)、(硬) 110g、1kg、15kg (組)



台灣 施敏打硬 股份有限公司
セメダイン

總公司：台北縣淡水鎮下莊路176-3號

電話：(02) 2629-1425 • 2629-1443

FAX：(02) 8631-6806

高雄分公司：高雄市三民區熟河二街14號

電話：(07) 3118198 • 3215686